

# ASPECTS CONCERNING THE OBTAINING OF NANOPARTICLES WITH BIOCIDES PROPERTIES BASED ON LIGNIN MODIFIED BY HYDROXYMETYLATION

## ASPECTE PRIVIND OBTINEREA DE NANOPARTICULE CU PROPRIETĂȚI BIOCIDICE PE BAZĂ DE LIGNINĂ MODIFICATĂ PRIN HIDROXIMETILARE

CĂPRARU Adina-Mirela<sup>1</sup>, TRINCĂ Lucia Carmen<sup>1</sup>, UNGUREANU Elena<sup>1</sup>,  
POPA V.I.<sup>2</sup>, MĂLUȚAN Th.<sup>2</sup>  
e-mail: amcapraru@yahoo.com

**Abstract.** In this paper are presented the results of a study concerning the obtaining and characterization of nanoparticles based on lignin modified by hydroxymethylation reaction and interaction between them and birch veneer. The lignin derivatives were synthesized using lignin from grass (grass Sarkanda) offered by the company Granit (Switzerland), in specific conditions to ensure the obtaining of nanoparticles. The birch veneer samples were successively immersed in copper (II) solutions and unmodified and modified lignin (5% concentration in 0.1 N ammonia solutions) in order to realize in situ complexes between the two partners. The biostability of veneer samples thus treated was assessed by their burial in soil for six months and was characterized by mass loss and contact angle values variations. The obtained results show that treatment of birch veneer with complexes of nanoparticles with copper provides high stability of the woody substrate.

**Key words:** lignin, nanoparticles, veneer, biocides, biostability.

**Rezumat.** În această lucrare sunt prezentate rezultatele unui studiu privind obținerea și caracterizarea nanoparticulelor pe bază de lignină modificată prin reacția de hidroximetilare și interacțiunea acestora cu furnirul de mesteacăn. Derivații de lignină au fost sintetizați din lignina din iarbă oferită de firma Granit (Elveția), în condiții specifice, pentru a asigura obținerea de nanoparticule. Probele de furnir de mesteacăn au fost imersate succesiv în soluții cuprice (II) și soluții de lignină nemodificată și modificată (concentrație de 5 % în soluție de amoniac 0,1 N), în scopul de a realiza un complex in situ între cei doi parteneri. Biostabilitatea probelor de furnir astfel tratate a fost evaluată prin îngroparea acestora în sol timp de șase luni și caracterizate prin variațiile pierderilor de masă și a valorilor unghiului de contact. Rezultatele obținute arată că tratamentul aplicat furnirului de mesteacăn cu complecși de cupru și nanoparticule de lignină oferă o stabilitate ridicată a substratului lemnos.

**Cuvinte cheie:** lignină, nanoparticule, furnir, biocizi, biostabilitate.

---

<sup>1</sup> University of Agricultural Sciences and Veterinary Medicine of Iași, Romania

<sup>2</sup> "Gheorghe Asachi" Technical University of Iasi, Romania

## INTRODUCTION

Lignin is a macromolecular compound more chemically active than cellulose or other natural polymers due to the functional groups contained in its macromolecule; being the main aromatic component of plant tissues, representing 20-40% of higher plants' mass it is located in the cellular wall and in intercellular spaces. Globally, lignin is regarded as a raw material with high recovery potential, accessible from renewable sources, with low costs and a negligible degree of pollution (Căpraru et al., 2008). The nanoparticles applicative impact is mainly important considering the wide range of fields identified so far: in medicine to provide drugs, new smart nano-sized coatings beginning to be used on an industrial scale, and also IT, auto, cosmetics, chemicals and packaging industries (Popa et al., 2011).

The researches in the lignin area, in the last decades, were focused not only on the extraction process but also on structures elucidation of products separated from different vegetal raw material, on chemical and reactivity characterization, functional properties and new application directions (Ungureanu et al., 2008). Lignin accessibility from renewable resources and its environment compatibility, lately enlarge the researches area in lignin modification reactions. The previous studies evidenced that the antimicrobial properties of aromatic polymers can be amplified through chemical modification and complexation with copper ions (Măluțan et al., 2007, 2008, Popa 1983, Căpraru et al., 2008, 2009). The favorable results previously obtained permitted the synthesis of nanoparticles from modified lignins through hydroxymethylation, in special reaction conditions (Schilling, 1993). The aim of this work was to test the capacity of nanoparticles obtained from different lignins and copper ions in ensuring birch veneer biostability (Yamaguchi et al., 2001, Matsushita et al., 2006). The results evidenced that in these conditions it was possible to assure a better interaction between lignin and wood by copper ions supplementations, which promoted the increasing of wood stability. Wood stability was quantified through mass loss and contact angle.

## MATERIAL AND METHOD

**Materials:** In this study we used the following materials: birch veneer samples sizes (1x10) cm, Sarkanda grass lignin, dissolved in 0.1 N ammonia solution, in 5% concentration (unmodified products - from Granite Company- Switzerland in the European research program-Ecobinders) and laboratory modified lignin by hydroxymethylation reaction under appropriate conditions to obtain nanoparticles, cupric chloride and cuproxam. To evaluate the biostability degree the birch veneer specimens treated with lignin derivatives and solutions containing copper ions were buried in soil for six months. The influence of treatments applied was monitored by mass loss and contact angle (measured of Kruss Goniometry).

### Methods

**1. The synthesis of nanoparticles by hydroxymetylation of lignins:** 10 g lignin were suspended in 47 mL of distilled water under stirring for two hours at room temperature. After obtaining the lignin suspension 1.29 g of 50 % NaOH solution were added and 3.14 g of 25 % NH<sub>4</sub>OH solution as a catalyst, and the mixture was shaken

for two hours. Afterwards, 6.7 g of 37 % formaldehyde were introduced in the system and the reaction was performed at 85 °C for 4h in a water bath. The resulted product was recovered by precipitation at pH 2 with 1N HCl solution and then it was separated by centrifugation. The solid phase was washed twice with distilled water and then dried and weighed (Schilling et al., 1993). The resulting product was subjected to nanoparticles dimensional distribution analysis using Multi Seiser.


## 2. Treatment of birch veneer samples with unmodified lignin, lignin-based nanoparticles and cupric solutions

We used birch veneer samples ( size 1x10 cm) for the treatment with lignin-based nanoparticles dissolved in 0.1 N ammonia solution at a concentration of 5 %, as following:

- Birch veneer samples were immersed in solutions containing copper ions (copper chloride or copper ammonia solutions) for 5 minutes, followed by drying at room temperature (laboratory conditions);
- Samples were immersed in unmodified and modified lignin solutions for five minutes and dried under mild conditions. The treated birch veneer samples were weighed before to determine the quantity of material retained on the surface of the samples and then they were buried in soil under laboratory conditions for a period of six months, with regular watering to maintain specific soil moisture. The degree of biodegradation was evaluated by determining the mass loss and the contact angle measured on the surface the birch veneer treated with lignin derivatives and copper solutions.

## RESULTS AND DISCUSSIONS

The possibilities of obtaining of nanoparticles based on ligins or its derivatives could, properly represent a new direction to study both applicative and fundamental character. In figure 1 it is presented the nanoparticle size distribution curve obtained in dimensional analysis of Sarkanda grass lignin submitted to modification.

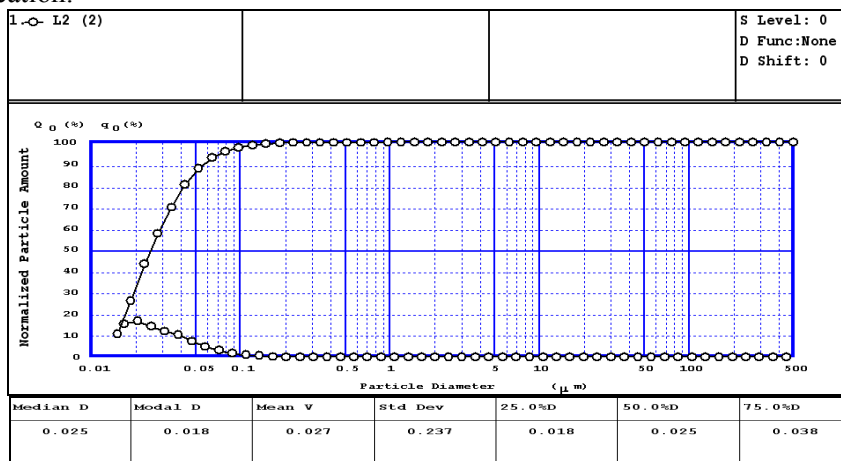


**Fig. 1** - Dimensional distribution curve for nanoparticles synthesized from hydroxymethylated grass lignin (L2)

Thus, it appears that the structural characteristic of lignin's used in the modified reaction induced different characteristics in nanoparticles size and distribution. In the case of grass lignin (L2) particles presented a lower average size and a more uniform distribution.

#### **Mass loss determination recorded for birch veneer samples treated with nanoparticles based on hydroxymethylated lignin**

The veneer samples were treated with nanoparticles based on hydroxymethylated lignin, with their copper complexes and with copper solutions ( $\text{CuCl}_2$  and Cuam). The biodegradation degree of samples thus obtained was determined by mass loss after burial in soil for six months.

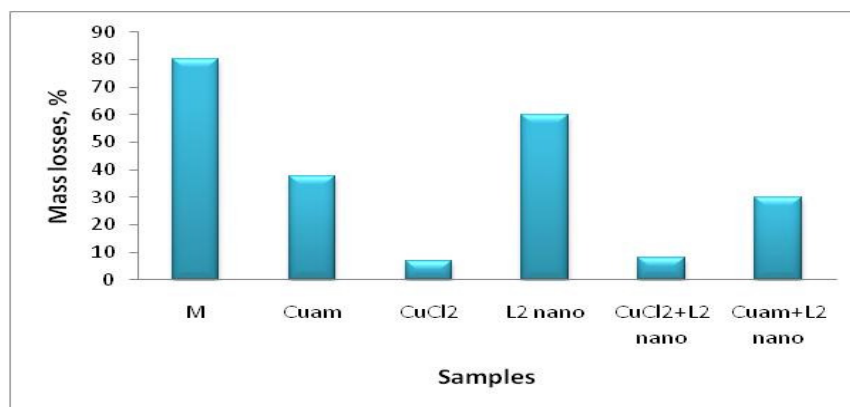


**Fig. 2 - Variation of mass loss for the birch veneer samples non-treated (M) and treated with  $\text{CuCl}_2$ , Cuam, L2nano,  $\text{CuCl}_2\text{L2nano}$ , CuamL2nano**

The data obtained for samples treated with lignin based nanoparticles and copper compounds show that the mass loss is lower compared to untreated samples. The lower mass loss was due to copper's toxic effects, to lignin's derivatives and to the two components' complexes, which limit and inhibit the microorganisms' attack.

The treatment of wood surface with copper containing solutions, especially when provided by the chloride derivative and the lignin nanoparticles, proved to be more efficient. This situation may be correlated with their various functionalities induced through hydroxymethylation, consequently resulting in different degrees of copper complex forming and wood surface interaction.

#### **Determination of contact angle of the veneer samples treated with nanoparticles based on hydroxymethylated lignin**


The contact angle values for veneer specimens, buried into the soil for six months, were done to monitor the efficiency of surface treatment and to establish the correlation between this parameter and weight loss recorded (fig. 3).

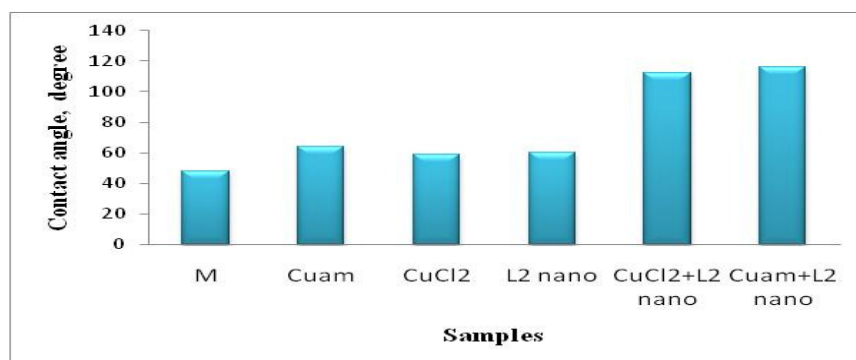


**Fig. 3** - Variation of contact angle for the veneer samples non-treated (M) and treated with Cuam, CuCl<sub>2</sub>, L2nano, CuCl<sub>2</sub>L2nano, CuamL2nano

The data showed that the contact angle reaches higher values (94 -116 °) in the case of samples treated with copper complexes lignin derivatives, compared with the control or with those samples for which it was used copper ions solutions or unmodified lignin.

Therefore, those treatments provide biological stability and hydrofobycity of wood surfaces due to the more efficient action of lignin nanoparticles in the presence of copper ions which were better fixed on wood support. That is how it was assured a better protection against microbiological attack. During the contact angle measurement, it was observed that the hydrophilic surface has a very low level, the drop of water in some cases penetrated the wood surface and its evolution showed insignificant variations in time (fig. 4 and 5).

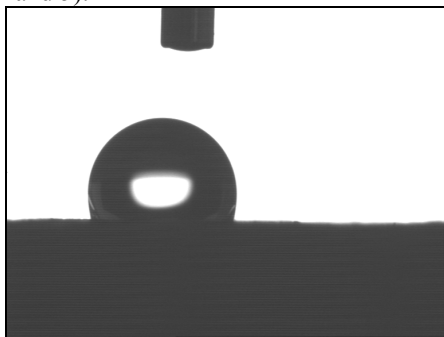

**Fig. 4** - The image of drop of water on the surface of birch veneer based nanoparticles treated lignin and copper solutions (Cuam+L2nano) measured of Kruss Goniometry

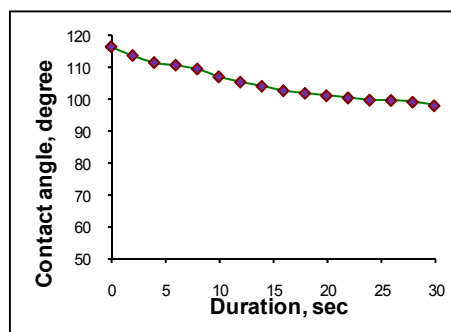

**Fig. 5** - Variation in time of contact angle of specimen surface of birch veneer treated with Cuam+ L2nano

The image of drop of water on the surface of birch veneer treated with nanoparticles based hydroxymethyl lignin and copper solution (Cuam+L2) is presented in figure 10. Water droplet stability was found at over 100 degrees for angle values registered. In figure 5 it could be observed the slow decrease of contact angle during the measurement for 30 seconds.

## CONCLUSIONS

1. A modified method of hydroxymethylation made possible the synthesis of nanoparticle from five types of lignin products from different sources with different reactivity capacity.
2. The nanoparticles obtained in hydroxymethylation were characterized by different dimensional size and distribution depending on studied lignin type.
3. Synthesized derivatives have been used to treated birch veneer in order to ensure its protection against microbiological attack followed by burial in soil samples for a period of six months.
4. The biological stability was assessed by determining mass loss and contact angle reported to the distilled water.
5. The data showed that the use of hydroxymethyl lignin-based nanoparticles and their complexes with copper provides good protection reducing mass losses and high values of contact angle. It was also observed certain hydrophobicity effects and a decreasing in the penetration level of water into the substrate timber.

## REFERENCES

1. Căpraru A.M., Ungureanu E., Popa V.I., 2009 - *Aspects concerning some biocides systems based on natural aromatic compounds aromatic compounds and their copper complexes*, 15<sup>TH</sup> International Symposium on Wood, Fibre and Pulping Chemistry, Norvegia;
2. Căpraru A.M., Ungureanu E., Popa V.I., 2008 - *Aspects concerning the interaction between birch veneer and different compounds with biocide potential action*, EEMJ, Vol. 7, No. 5, p. 525-530;
3. Măluțan T., Popa V.I., 2007 - *Poteția lemnului prin metode specifice*, Ed. Cermi, Iași;
4. Măluțan Th., Nicu R., Popa V.I., 2008 - *Contribution to the study of hydroxymethylation reaction of alkali lignin*, Bio/Resources, 3(1), p. 13-20;
5. Matsushita Y., Wada S., Fukushima K., Yasuda S., 2006 - *Surface characteristics of phenol formaldehyde–lignin resin determined by contact angle measurement and inverse gas chromatography*, Industrial Crops and Products 23, p. 115–121;
6. Popa V.I., 1983 - *Tehnologii de valorificare a ligninei*, Institutul Politehnic Iași, p. 11-13;
7. Popa V.I., Căpraru A.M., Grama S., Măluțan Th., 2011 - *Nanoparticles based on modified lignins with biocide properties*, Cellulose Chem. Technol., 45 (3-4), p. 221-226.
8. Schilling P., 1993 - *Submicron lignin-based binders for water-based black ink formulation*, United States Patent, no. 5,p. 192,361;
9. Ungureanu E., Căpraru A.M., Popa V.I., 2008 - *Aspects concerning some bioprotection agents based on natural aromatic compounds and their copper complexes*, COST E-50/ILI joint meeting, October, 27-29 Switzerland, p. 40;
10. Yamaguchi H., Yaoshino K., 2001 - *Influence of Tannin-copper Complexes as Preservatives for Wood on Mechanism of Decomposition by Brown-Rot Fungus Fomitopsis palustris*, Holzforschung, 55(5), p. 4644-4700;